

Abrupt Change of Josephson Plasma Frequency at the Phase Boundary of the Bragg Glass in $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_{8+\delta}$

M.B. Gaifullin¹, Yuji Matsuda^{1,†}, N. Chikumoto², J. Shimoyama³ and K. Kishio³

¹*Institute for Solid State Physics, University of Tokyo, Roppongi 7-22-1, Minato-ku, Tokyo 106, Japan*

²*Superconductivity Research Laboratory, ISTEK, Shibaura 1-16-25, Minato-ku, Tokyo 105, Japan*

³*Department of Superconductivity, University of Tokyo, Bunkyo-ku, Tokyo 113, Japan*

(received 16 December 1999)

We report the first detailed and quantitative study of the Josephson coupling energy in the vortex liquid, Bragg glass and vortex glass phases of $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_{8+\delta}$ by the Josephson plasma resonance. The measurements revealed distinct features in the T - and H -dependencies of the plasma frequency ω_{pl} for each of these three vortex phases. When going across either the Bragg-to-vortex glass or the Bragg-to-liquid transition line, ω_{pl} shows a dramatic change. We provide a quantitative discussion on the properties of these phase transitions, including the first order nature of the Bragg-to-vortex glass transition.

74.25.Nf, 74.50+r, 74.60.Ec, 74.72.Hs

The vortex matter in high- T_c superconductors exhibits a fascinatingly rich phase diagram with a variety of phase transitions. There, thermal fluctuation and disorder alter dramatically the vortex phase diagram which has been observed in the conventional superconductors. At high temperature, the strong thermal fluctuation melts a vortex lattice into a vortex liquid well below the upper critical field. On the other hand, at low temperature or low field where the vortex liquid freezes into a solid phase, disorder plays an important role. The disorder is known to destroy the long-range order of the Abrikosov lattice [1]. Recent investigations have revealed that the vortex solid phase is comprised of two distinct phases; a highly disordered phase at high field and a rather ordered phase at low field [2–4]. The former phase is the vortex glass or entangled solid phase which is characterized by divergent barriers for vortex motion [5]. The latter phase is the Bragg glass or quasilattice phase in which no dislocation exists and quasi-long-range translational order is preserved [6]. In very clean single crystals, thermodynamical measurements have revealed that the Bragg glass undergoes a first order transition (FOT) to the vortex liquid [7–9]. The transition from the Bragg glass to the vortex glass, on the other hand, is characterized by the second magnetization peak at which the critical current shows a sharp increase [4]. It was proposed that the crossover from the FOT to the second peak regime is governed by a critical point T_{cp} in the phase diagram, which in $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_{8+\delta}$ is located near 40 K. While the nature of the vortex liquid has been extensively studied, the properties of the Bragg glass and the nature of the thermally induced FOT from the Bragg glass to the vortex liquid are still not quite understood. Moreover, the phase transition from the Bragg glass to the vortex glass at lower temperatures has been a longstanding issue, though this transition is proposed to be disorder driven, caused by competition between the elastic

and pinning energies [4,10–14]. A major obstacle has been that most of the previous experiments had to been performed under a strongly nonequilibrium condition because most part of the Bragg and vortex glasses are located deep inside the irreversibility line T_{irr} .

The most direct way to clarify the nature of these phases and the phase transitions among them is to measure the interlayer phase coherence for each vortex phases, because the CuO_2 layers are connected by the Josephson effect. One of the most powerful probes for the interlayer phase coherence is the Josephson plasma resonance (JPR) which provides a direct measurement of the Josephson plasma frequency ω_{pl} related to the maximum Josephson critical current $j_J = \varepsilon_0 \Phi_0 \omega_{pl}^2 / 8\pi^2 c d$ and the Josephson coupling energy $U_J = \Phi_0 j_J / 2\pi c$, where ε_0 and d are the dielectric constant and interlayer spacing, respectively. [15–22]. Especially in $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_{8+\delta}$ with large anisotropy, a very precise determination of ω_{pl} is possible because ω_{pl} falls within the microwave window.

All of the JPR measurements of $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_{8+\delta}$ up to now have been carried out in the cavity resonator by reducing ω_{pl} by H [15–17]. Unfortunately, sweeping H below T_{irr} drives the vortex system into a strongly nonequilibrium state due to the Bean critical current induced by the field gradient inside the crystal, as was demonstrated in Refs. [16] and [23]. Therefore, in order to investigate the Bragg and vortex glass phases, it is crucial to measure the JPR as a function of the microwave frequency ω_{pl} while holding H at a constant value. In this Letter, we report the first detailed and quantitative study of the Josephson coupling energy in the Bragg glass, the vortex glass and the vortex liquid phases and the phase transitions among them by the JPR which has been performed by sweeping ω continuously. The measurements revealed distinct features in the T - and H -dependencies of ω_{pl} for each of the three different vortex phases. When going across either the Bragg-to-vortex glass

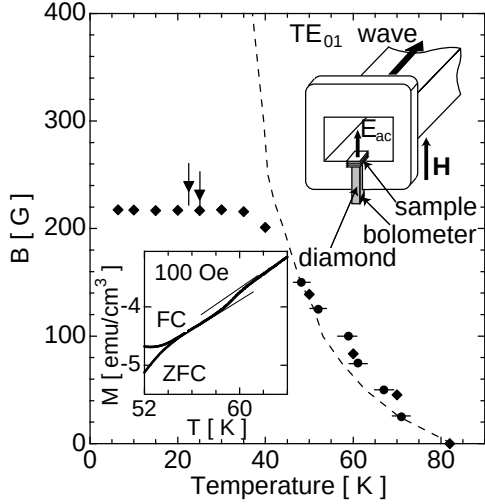


FIG. 1. Vortex phase diagram determined by the magnetization and the JPR. The filled circles represent H_m determined by the magnetization step (see inset). The filled triangles represent H_{sp} . The filled diamonds represent the field at which ω_{pl} shows an abrupt change. The dashed line is the irreversibility line. Lower inset: Magnetization measured in the field cooling (FC) and zero field cooling (ZFC) conditions. Upper inset: Bolometric detection of the microwave absorption. The crystal is supported inside the waveguide by a thermally isolated diamond plank ($\mathbf{H} \parallel c$). The JPR is caused by the microwave electric field $\mathbf{E}_{ac} \parallel c$.

or the Bragg-to-liquid transition line, ω_{pl} shows a dramatic change. We provide a quantitative discussion on the nature of these phase transitions in the light of these results.

All experiments were performed on a slightly underdoped $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_{8+\delta}$ single crystals ($T_c=82.5$ K) with dimensions $1.2 \times 0.5 \times 0.03\text{mm}^3$ grown by the traveling floating zone method. The inset of Fig.1 shows a typical magnetization step measured by SQUID magnetometer which can be attributed to the FOT of the vortex lattice. This FOT terminates at ≈ 40 K and the step is followed by the second magnetization peak located at ~ 230 Oe. Figure 1 shows the phase diagram obtained by the magnetization measurements. The JPR is measured by sweeping ω continuously from 20 GHz to 150 GHz [21]. The sample was placed at the center of the broad wall of the waveguide in the traveling wave TE_{01} mode. We used a bolometric technique to detect very small microwave absorption by the sample and employed a leveling loop technique to keep the microwave power constant when sweeping frequency. For this crystal $\omega_{pl}=125$ GHz at $T=0$, corresponding to the anisotropy parameter $\gamma = \lambda_c/\lambda_{ab} \approx 550$, where λ_{ab} and λ_c are the in-plane and out-of-plane penetration lengths, respectively. Here we used $\lambda_{ab} \approx 200$ nm and $\lambda_c = c/\omega_{pl}\sqrt{\epsilon_0} \approx 110$ μm . We determined $\epsilon_0 = 11.5 \pm 1$ from the dispersion of the transverse plasma mode. All

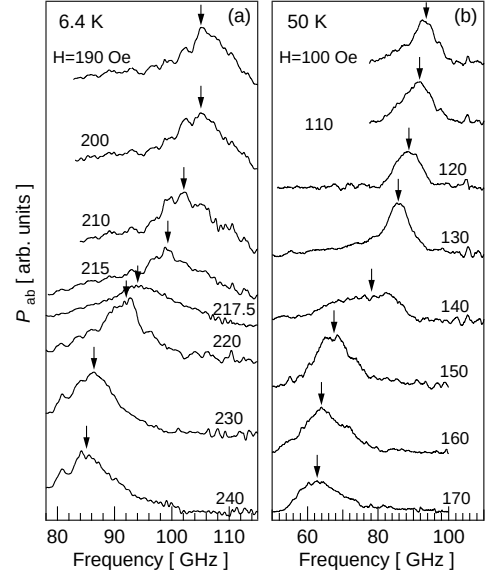


FIG. 2. The JPR as a function of frequency when crossing (a) the second peak (6.4 K) and (b) the FOT (50 K). We picked up only the longitudinal plasma mode which is sample size independent. The arrows indicate the peak position.

JPR measurements were performed in $\mathbf{H} \parallel c$ under the field cooling condition (FCC) where the field is very uniform. In this condition, the system is in equilibrium or at worst is trapped in a metastable state which we expect should be much closer to equilibrium compared to the state obtained in the field sweeping condition (FSC). In fact, while the resonance frequency below T_{irr} did not change at all with time for more than 48 hours in the FCC, it increases gradually with time in the FSC. We also confirmed that the resonance curves are exactly the same in different cooling cycles.

Figures 2(a) and (b) depict the resonant absorption as a function of ω when crossing the second peak field H_{sp} and the FOT field H_m , respectively. When ω coincides with ω_{pl} , the resonant absorption of the microwave occurs. These are the JPR measured in the Bragg and vortex glass phases under the FCC for the first time. In the magnetic field, ω_{pl} can be written as [18]

$$\omega_{pl}^2(B, T) = \omega_{pl}^2(0, T) \langle \cos \phi_{n,n+1} \rangle. \quad (1)$$

Here $\langle \cos \phi_{n,n+1} \rangle$ represents the thermal and disorder average of the cosine of the gauge invariant phase difference between layer n and $n+1$. If the vortex forms a straight line along the c -axis, $\langle \cos \phi_{n,n+1} \rangle$ is unity. The reduction of $\langle \cos \phi_{n,n+1} \rangle$ from unity is caused by the Josephson strings that are created by the deviation from the straight alignment of the pancake vortices along the c -axis. Thus ω_{pl} gives a direct information on the vortex alignment and therefore the phase transition of the vortex matter. After gradual decrease with H at lower H , ω_{pl} shows a sharp decrease in the field range between 215 Oe and 220 Oe at 6.5 K and between 140 Oe and

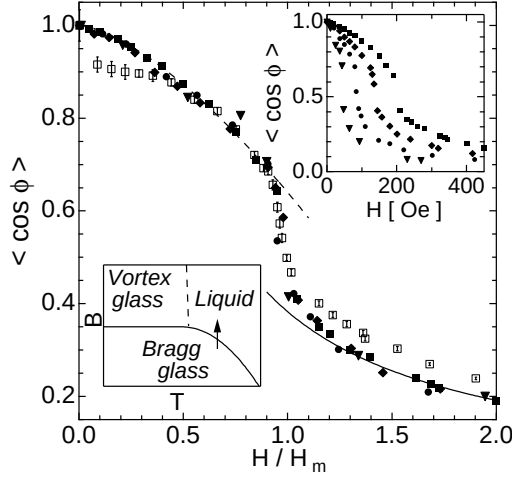


FIG. 3. Inset: H -dependence of $\langle \cos \phi_{n,n+1} \rangle$ when going across the FOT at high temperatures. Solid squares, diamonds, circles, and triangles show the data at 40 K, 50 K, 60 K, and 70 K respectively. Main panel: Same data plotted as a function of H/H_m . Open squares show $\langle \cos \phi_{n,n+1} \rangle$ as a function of H/H_{sp} at 30 K when crossing the second peak. The dashed line is the result of Eq.2. The solid line is the fit to Eq.3.

160 Oe at 50 K. At 217.5 Oe in Fig.2(a) and at 150 Oe in Fig.2(b), the resonance lines become broader, indicating a very rapid change of ω_{pl} with H . At higher H , ω_{pl} again decreases gradually. In Fig.1, we plot the fields at which ω_{pl} shows an abrupt change. These fields coincide well with the second peak and FOT fields determined by magnetization measurements.

We first discuss the resonance when going across the FOT. The inset of Fig.3 depicts the H -dependence of $\langle \cos \phi_{n,n+1} \rangle$ obtained from $\omega_{pl}^2(B, T)/\omega_{pl}^2(0, T)$. Although similar results have been reported [16,17], quantitative analysis was very difficult because the JPR measurements in the Bragg glass had been done under the strongly nonequilibrium condition, as we have already mentioned. Figure 3 depicts $\langle \cos \phi_{n,n+1} \rangle$ as a function of H normalized by H_m . Interestingly, $\langle \cos \phi_{n,n+1} \rangle$ exhibits very similar H/H_m -dependence at all temperatures. Obviously, the H -dependence of $\langle \cos \phi_{n,n+1} \rangle$ above FOT is very different from that below FOT; the curvature changes from negative to positive. We found that $\langle \cos \phi_{n,n+1} \rangle$ in the Bragg glass phase can be fitted as,

$$\langle \cos \phi_{n,n+1} \rangle = 1 - A_1 \frac{H}{H_m} - A_2 \left(\frac{H}{H_m} \right)^2, \quad (2)$$

with $A_1=0.16$ and $A_2=0.19$ above 40 K as shown in the dashed line in Fig.3. On the other hand, according to high temperature expansion theory [19], $\langle \cos \phi_{n,n+1} \rangle$ in the liquid phase above FOT can be written as,

$$\langle \cos \phi_{n,n+1} \rangle = \frac{U_J \Phi_0}{2k_B T H}, \quad (3)$$

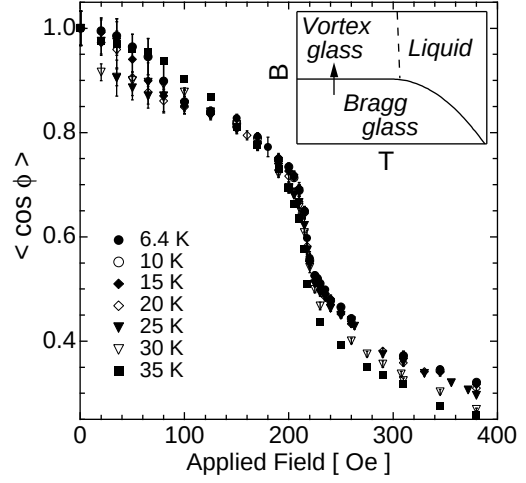


FIG. 4. H -dependence of $\langle \cos \phi_{n,n+1} \rangle$ when going across the Bragg-to-vortex glass transition at low temperatures.

when the Josephson energy is negligible compared with the energy of thermal fluctuations, *i.e.* $U_J \ll k_B T H / \Phi_0$. It has been shown experimentally that $\langle \cos \phi_{n,n+1} \rangle$ is inversely proportional to H in the liquid phase [15–17]. The present results provide a further rigorous test to Eq.3, because we now have no ambiguous fitting parameter and also have the data of the very detailed H -dependence of $\langle \cos \phi_{n,n+1} \rangle$ obtained by sweeping ω . The solid line in Fig.3 shows the result of the calculation. In the calculation, we used $\epsilon_0=12.0$. The fit to the data is excellent in the whole H -range at $H > 1.2H_m$, indicating that the vortex liquid is decoupled on the scale of the inter-layer distance. Small deviation from Eq.3 is observed at $H \leq 1.2H_m$. This suggests that the vortex-vortex correlation effect in the ab -plane which gives rise to the deviation from $1/H$ -dependence of $\langle \cos \phi_{n,n+1} \rangle$ in the liquid phase is important just above the FOT [22].

At H_m , $\langle \cos \phi_{n,n+1} \rangle$ is reduced to ≈ 0.7 at all temperatures, showing an occurrence of large vortex wandering in the Bragg glass. Near T_c , we note that ω_{pl} at $H=0$ is already suppressed by the phase fluctuations. If this effect is taken into account, it is expected that $\langle \cos \phi_{n,n+1} \rangle$ at H_m slowly increases with T , indicating that the melting becomes more linelike at higher T . The values of $\langle \cos \phi_{n,n+1} \rangle$ at H_m are close to the recent results of computer simulations for systems with small anisotropies [9].

The internal energy U experiences a jump ΔU at the FOT. This latent heat ΔU can be represented as a sum of the jumps in the in-plane energy, in the electromagnetic coupling energy, and in the Josephson energy ΔU_J [9]. To understand the nature of the FOT in detail, it is important to establish the relative jump in Josephson energy $\Delta U_J / \Delta U$. At 60 K, $\Delta U_J / T$ can be estimated to be $\approx 0.21k_B$ from $\langle \cos \phi_{n,n+1} \rangle$ which drops approximately from 0.70 to 0.45. On the other hand, $\Delta U / T$ at 60 K obtained from the magnetization step ΔM using

the Clausius-Clapeyron relation,

$$\Delta U/T_m = \Delta S = -d\Phi_0 \frac{\Delta M}{B_m} \frac{dB_m}{dT}, \quad (4)$$

is $\approx 1.34k_B$. Here ΔS is the entropy jump at the FOT point (T_m , B_m). Thus we find that ΔU_J constitutes approximately 16% of the latent heat, showing that ΔU_J occupies a substantial part of the latent heat at the FOT even in $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_{8+\delta}$ with very large anisotropy.

We now move on to the subject of the Josephson coupling at low temperatures when going across the transition from the Bragg glass to the vortex glass. Figure 4 shows the H -dependence of $\langle \cos \phi_{n,n+1} \rangle$ below 35 K. Below 100 Oe, $\langle \cos \phi_{n,n+1} \rangle$ shows a hump structure which may be related with the lower critical field. Above 100 Oe, the H -dependence of $\langle \cos \phi_{n,n+1} \rangle$ is very similar to that at high T when crossing the FOT. At all temperatures, $\langle \cos \phi_{n,n+1} \rangle$ shows an abrupt change at the second peak field $H_{sp} \approx 220$ Oe. In similarity to the high temperature behavior, the H -dependence of $\langle \cos \phi_{n,n+1} \rangle$ below and above H_{sp} are very different, showing clearly that H_{sp} separates two distinct vortex phases. In a very narrow field interval less than 5 Oe at H_{sp} , $\langle \cos \phi_{n,n+1} \rangle$ drops from approximately 0.7 to 0.5 (see also Fig.1(a)), corresponding to a nearly 20%-reduction of U_J . This strong reduction of $\langle \cos \phi_{n,n+1} \rangle$ provides a direct evidence of the decoupling nature of the Bragg-to-vortex glass transition [13]. At H_{sp} , $\langle \cos \phi_{n,n+1} \rangle$ is reduced to ≈ 0.7 from the zero field value similar to that below FOT. Although we do not show here, $\langle \cos \phi_{n,n+1} \rangle$ in the vortex glass phase deviates from the $1/H$ dependence in the whole B -regime above H_{sp} , which is to be contrasted to the behavior in the vortex liquid phase.

We finally discuss the phase transition from the Bragg glass to the vortex glass inferred from the JPR. The first question is the order of the transition. The abrupt change of $\langle \cos \phi_{n,n+1} \rangle$ shown in Figs.3 and 4 provides a direct evidence of the abrupt changes of the c -axis correlation length of the pancakes and of U_J which composes a substantial part in the free energy. In Fig.3 we plot the change of $\langle \cos \phi_{n,n+1} \rangle$ at H_{sp} ($T=30$ K), for the comparison with the change of the same quantity at the FOT. *The change of $\langle \cos \phi_{n,n+1} \rangle$ at H_{sp} is comparable or even sharper than that at the FOT.* This fact strongly indicates the first order nature of the phase transition from the Bragg glass to the vortex glass. The second issue is the critical point T_{cp} of the FOT which has been proposed to terminate at ≈ 40 K [4,7]. This proposal was made from the observation that ΔS becomes extremely small which can be seen from the T -independence of FOT line below T_{cp} . However, the vanishing of ΔS does not immediately imply the termination of the FOT, which suggests that the issue of the termination is nontrivial. As seen in Figs.3 and 4, there is no discernible difference in the H -dependence of $\langle \cos \phi_{n,n+1} \rangle$ as we go through the Bragg-to-liquid transition regime, into the Bragg-to-vortex glass

transition regime, except for a gradual decrease of the change of $\langle \cos \phi_{n,n+1} \rangle$ at the transition. These results imply that the FOT does not terminate at ≈ 40 K, but that there is no critical point or the FOT persists at least below 6.4 K. We note that a similar conclusion has been reached very recently using the magneto-optical imaging technique [24].

In summary, we have performed the JPR experiments in the Bragg glass, vortex glass, and vortex liquid phases in the FCC. We found an abrupt change in the Josephson coupling energy when going across either the FOT line or the second magnetization peak line. We showed that this change occupies a substantial part of the latent heat at the FOT. The results suggest that the Bragg-to-vortex glass transition is first order in nature and that the critical point of the FOT does not terminate at ≈ 40 K.

We thank B. Horovitz, X. Hu, Y. Kato, P.H. Kes, T. Onogi, A. Sudbø, and A. Tanaka for discussions. We are indebted to L.N. Bulaevskii for several valuable comments. We also thank A.E.Koshelev for the critical reading of the manuscript.

† Corresponding author,

E-mail Address :ym@issp.u-tokyo.ac.jp

- [1] A.I. Larkin, and Y.N. Ovchinnikov, JETP **38**, 854 (1974).
- [2] N. Chikumoto *et al.*, Phys. Rev. Lett. **69**, 1260 (1992)
- [3] R. Cubitt *et al.*, Nature (London), **365**, 407 (1993).
- [4] B. Khaykovich *et al.*, Phys. Rev. Lett. **76**, 2555 (1996); Phys. Rev. B **56**, R517 (1997).
- [5] D.S. Fisher *et al.*, Phys. Rev. B **43**, 130 (1991).
- [6] T. Giamarchi, and P.Le Doussal, Phys. Rev. B **55**, 6577 (1997).
- [7] E. Zeldov *et al.*, Nature (London), **375**, 373 (1995), A. Shilling *et al.*, Nature (London) **382**, 791 (1996).
- [8] M.J.W. Dodgson *et al.*, Phys. Rev. Lett. **80**, 837 (1998).
- [9] X. Hu *et al.*, Phys. Rev. Lett. **79**, 3498 (1997), A.E. Koshelev, Phys. Rev. B **56**, 11201 (1997), A.K. Nguyen and Sudbø, Phys. Rev. B **58**, 2802 (1998), Y. Nonomura, and X. Hu, Physica B in press.
- [10] D.Ertas and D.R. Nelson, Physica C **272**, 79 (1996).
- [11] S. Ryu *et al.* Phys. Rev. Lett. **77**, 2300 (1996).
- [12] V. Vinokur *et al.*, Physica C **295**, 209 (1998).
- [13] B. Horovitz and T.R. Goldin, Phys. Rev. Lett. **80**, 1734 (1998), B. Horovitz, Phys. Rev. B **60**, R9939 (1999).
- [14] A.E. Koshelev and V.M. Vinokur, Phys. Rev. B **57**, 8026 (1998).
- [15] Y. Matsuda *et al.*, Phys. Rev. Lett., **75**, 4512 (1995), O.K.C. Tsui *et al.* Phys. Rev. Lett. **76**, 819 (1996)
- [16] Y. Matsuda *et al.* Phys. Rev. Lett. **78**, 1972 (1997).
- [17] T. Shibauchi *et al.*, Phys. Rev. Lett. **83**, 1010 (1999).
- [18] L.N. Bulaevskii *et al.*, Phys. Rev. Lett. **74**, 801 (1995).
- [19] A.E.Koshelev, Phys. Rev. Lett. **77**, 3901 (1996).

- [20] I.J. Hwang and D. Stroud, Phys. Rev. B **59**, 3896 (1999).
- [21] M.B. Gaifullin *et al.* Phys. Rev. Lett. **83**, 3928 (1999).
- [22] A.E. Koshelev, L.N. Bulaevskii, and M.P. Maley, Phys. Rev. Lett. **81**, 902 (1998).
- [23] E. Rodrigues *et al.*, Phys. Rev. Lett. **71**, 3375 (1993).
- [24] C.J. van der Beek *et al.*, cond-mat/9912276.